SOUTHWEST RESEARCH INSTITUTE®

Fuels and Lubricants Research Division

NMMA CE50S Lubricity Test (ASTM D4863)

Specifications

• NMMA TC-W3®

Objective

• Evaluate the lubricity of a lubricant for a two-stroke cycle air-cooled engine.

Field Service Simulated

• Operation of all two-stroke cycle outboard engines.

Test Fixture

- A Yamaha CE50S single-cylinder, air-cooled, two-stroke cycle, spark-ignition engine is coupled to a high-speed 10-hp dynamometer.
- External cooling air is supplied to the engine by a variable delivery fan.

Test Parameters

- A test consists of three sets of five to seven piston "tightenings." In a tightening, the torque decrease is measured as the spark plug gasket temperature increases from 200°C to 300°C.
- Each tightening begins with a stabilization period at the following conditions:

Parameter	Value
Engine speed, rpm	4000
Load	WOT
Spark plug gasket temp, °C	200
Fuel/lubricant ratio	150:1



- After stabilization, the cooling air is stopped and the torque decrease is monitored as the spark plug gasket temperature rises.
- Cooling air is restored when the spark plug gasket temperature reaches 350°C.
- This procedure is repeated five times in each of two sets on both the reference and candidate lubricants.

Test Parts Evaluation

· General engine condition is evaluated.

Used Lubricant Analysis

• None.

Pass/Fail Criteria

• The torque decrease of the candidate lubricant must be less than or equal to NMMA XPA-3259 reference lubricant at the 90% confidence level.

• We welcome your inquiries. For additional information, please contact:

Patrick Lang

Manager 210.522.2820 patrick.lang@swri.org


Fuels and Lubricants Research Division

Southwest Research Institute 6220 Culebra Road San Antonio, Texas 78238-5166

swri.org lubricanttesting.swri.org





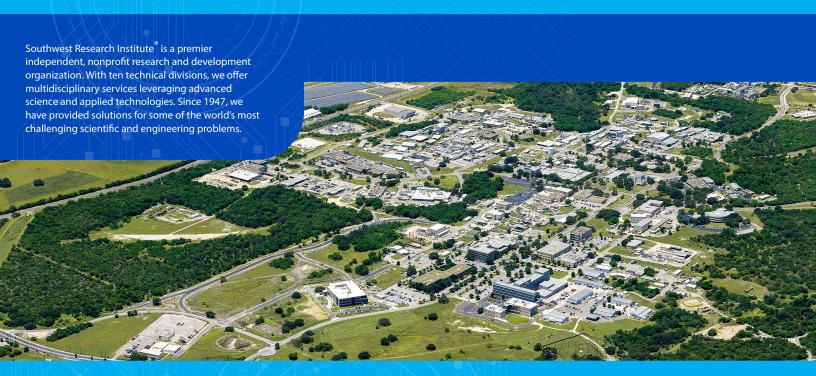



Benefiting government, industry and the public through innovative science and technology

210.522.2122

ask@swri.org

Like. Share. Follow. Listen.





swri.org